

Compositional Studies of Ancient Copper from Romanian Territories

Agata Olariu^{*} C. Besliu[°], M. Belc[⊕],

I. V. Popescu^{*}, T. Badica^{*},

Gh. Lazarovici[◇]

^{}National Institute for Physics and Nuclear Engineering,*

Bucharest, Romania

[°]Faculty of Physics, Bucharest

[⊕]Physics Department, Ovidius University, Constața, Romania

[◇]History Museum of Transylvania, Cluj-Napoca, Romania

Abstract

Ancient copper objects from Romanian Territories have been analyzed by neutron activation analysis. A series of elements is determined: Au, Ag, As, Co, Cr, Fe, Hg, Ni, Zn, Sb, Sc, Se, Sn. Using mathematical dendograms some classifications and correlation have been established.

1 Introduction

The importance of analyses of archaeological objects is well known, the elemental composition coming to complete the knowledge on the archaeological objects: style, typology, place of discover, culture, dating, data got by pure historical arguments. Processing the compositional scheme of historic objects one can obtain the identification of the materials and different characterizations and classifications of the finds.

As concerns the ancient copper, the elemental structure shows first of all the bronzes: copper + arsenic, copper + antimony, copper + tin or incidentally copper + zinc. Trace elements could also help to the understanding of copper items: objects with closed elemental composition could be put in cultural or temporal synchronization. From the all the analytical methods for copper neutron activation analysis (NAA) seems to be the best single method ¹ offering enough analytical capabilities to provide a good data base. For provenance studies, which it is a very complicated problem the method to apply is the atomic mass spectroscopy: what it remained constant from the ores to the final metal objects is the ratio of lead, determined by the atomic mass spectroscopy: Pb^{208}/Pb^{206} and Pb^{207}/Pb^{206} ²⁻⁵.

In this paper we have analyzed by neutron activation analysis a lot of 41 Neolithic copper objects: axes, needles, daggers and others objects from the National History Museum of Transylvania, Cluj-Napoca, Romania. In Table 1 it is given the list of analyzed samples.

2 Experimental method of analysis

Sampling. First some corroded parts have been removed from the surface of copper objects, the corroded material having a totally different elemental composition from that of the body of the object. Then samples of 10-50 mg have been cut with a hard vidia knife from the object body and after that washed with different solvents: acetone, benzene, ether to avoid the impurities from the surface of the item and the protective varnish, added in the museum.

Irradiation of medium periods. Samples have been put in polyethylene foils and irradiated at the rabbit system of the nuclear reactor VVR-S, from NIPNE Magurele, Bucharest at the flux of $\approx 1.2 \times 10^{12}$ neutrons/cm²·sec, for 30 minutes. Copper being in majority it was strongly activated so that the induced radioactivity in the samples could be measured only after 4-5 days . Natural cooper has 2 isotopes: Cu⁶³ and Cu⁶⁵ which by the reaction (n, γ) give the radioisotopes Cu⁶⁴ T_{1/2}=12.74 h and Cu⁶⁶ with T_{1/2}=5.10 min. After a cooling time of 4-5 days, in the gamma spectra of the samples, the activity coming from the photopeak of 1345.8 keV (0.0048) of Cu⁶⁴ is small enough and permits to remark other elements, present in the cooper matrix. The samples have been measured 1000 s at a spectrometric chain using a Ge(Li) detector of 135 cm³ and an analyzer of 4096 channels coupled at a PC. The system gave a resolution of 2.7 keV at 1.33 keV (Co⁶⁰). We observed the elements: Au, As, Cu and Sb.

Long time irradiation: The samples of copper have been wrapped in aluminum foil and put it in a quartz phial together with metallic spectroscopic pure standards, copper and nickel and irradiated at the vertical chain of the reactor, at a flux of $\approx 10^{13}$ neutrons/cm²·sec, for a period of time of 40 h. After a cooling time of 2 weeks, we measured the γ activity of the samples at the same spectrometric chain, for 3000 s. We have determined the following elements:

Sb, Ag, Co, Cr, Fe, Hg, Ni, Se, Sn.

Cobalt. Cobalt was determined in the copper object using the isotope Co^{60} got in the reaction: $\text{Co}^{59}(\text{n}, \gamma)\text{Co}^{60}$. Co^{60} is also produced by the reaction: $\text{Cu}^{63}(\text{n}, \alpha)\text{Co}^{60}$ which is important enough in this situation, when the element copper is the major element ($\approx 99\%$). So that $C_{\text{Co}} = C_{\text{total}} - C_{\text{Co-Cu}}$, where C is the concentration. Another correction made in the calculus of the cobalt concentration in the copper samples is that the used copper standard contains also traces of cobalt. It was determined that a standard of pure copper has a content of minimum 4 ppm of cobalt. Also in the gamma background of the experimental room it were observed the peaks at the cobalt energies of 1773.2 keV and 1332.5 keV; therefore from the respective photopeaks area it was subtracted the area given by the background, measured for the same period of time as the sample.

Mercury was determined from the γ ray of 279.2 keV and intensity (81.5%) of Hg^{203} with $T_{1/2} = 46.60\text{d}$. This ray is interposed with the γ ray from Se^{75} , of 279.5 keV, and intensity 0.25. Therefore the contribution of the mercury must be extracted from the peak of peak of 279 keV: $N_{\text{Hg}^{203}} = N_{\text{total}279\text{keV}} - N_{\text{Se}^{75}}$, where $N_{\text{Hg}^{203}}$ is the counting rate in the peak of 279 keV, given by mercury contribution. $N_{\text{total}279\text{keV}}$ is the total counting rate in the peak of 279 keV $N_{\text{Se}^{75}}$ is the counting rate in the peak of 279 keV, due to the selenium presence. It was used as reference the selenium peak from the energy 264.7 keV of intensity of 0.5658 :

$\epsilon_{264\text{keV}} \cdot S_{264\text{keVSe}^{75}} \cdot N_{264\text{keVSe}^{75}} = \epsilon_{279\text{keV}} \cdot S_{279\text{keVSe}^{75}} \cdot N_{279\text{keVSe}^{75}}$ where: $\epsilon_{264\text{keV}}$ is the efficiency of the detector from 264 keV, $\epsilon_{279\text{keV}}$, is the efficiency at the energy of 279 keV, $S_{264\text{keVSe}^{75}}$, the intensity of the line of 264 keV of Se^{75} , $S_{279\text{keVSe}^{75}}$, the intensity of the line of 279 keV of Se^{75}

Nickel. The concentration of nickel was measured by the isotope Co^{58} ($T_{1/2} = 71.3\text{d}$). Nickel was a exception by the fact that it was determined by the reaction

$\text{Ni}^{58}(\text{n}, \text{p})\text{Co}^{58}$, unlike the other elements determined by the reaction (n, γ) . In the Table 2 are given the results of activation analysis for the Prehistoric copper object, from the National Museum of History from Cluj-Napoca. The concentrations are given in ppm, and when an element was determined in a quantity larger than 10000 ppm, its concentrations was expressed in percents, using the notation of %. The measured errors were the statistical errors and were in mean of $<10\%$.

3 Results and discussions

First of all one distinguishes from the Table 2 the samples of copper which contain also other elements than copper, in concentrations higher of 1%, the copper based-alloys. So that we can distinguish the items:

LG10 1.11% Sn, LG14 2.61% As, LG15 1.68% As, LG22 2.82% Sn + 2.07% Zn, LG41 1.53% As.

Arsenical-copper The presence of arsenic in the samples of ancient copper is shown in Fig. 1, the analyzed objects could be structured on 4 levels of concentrations:

- concentrations of As < 100 ppm: LG1, LG9, LG11, LG12, LG13, LG24, LG31
- concentrations between 100 ppm and 1000 ppm: LG5, LG8, LG21
- concentrations between 1000 ppm and 1%: LG10, LG16, LG22, LG37, LG38, LG39
- concentrations $> 1\%$: LG14, LG15 and LG41

The concentrations of arsenic could be interpreted in the sense that the samples are made manufactured by the ore of type reduced, like sulfurs and not deliberated alloyed. The specified ores needs a higher degree of metallurgy level to produce the metal. The fact that the items LG14, LG15, LG41 which contain

arsenic in concentrations higher of 1% to be manufactured from a reduced ore type is possible with a probability of 3%⁶, in the rest of chances the arsenic being added intentionally, consciously to obtain some artifacts of copper with superior properties than those items of pure copper, the arsenical bronzes^{7,8}.

As concerning the samples LG16 and LG37, LG38, LG39 with a content of arsenic of about 1000 ppm, one can do the same discussion but the probability of bringing in close association of the object to a ore of reduced type is in this case 13%. Zvi Goffer⁹ gives another interpretation and method to establish the affiliation of studied objects at the type of arsenic-copper. The Sb and Ag contents of some arsenical copper objects analyzed by Zvi Goffer are directly proportional to the As content. As, Sb and Ag are associated with Cu only in sulfoarsenate ores. The presence of these elements is thus indicative that sulfoarsenate ores must have been deliberately added during the manufacturing process. For the analyzed Neolithic copper from Transylvanian territories we have represented in Fig. 2 the two dependencies indicated in ref.7: $C_{As} - C_{Ag}$ and $C_{As} - C_{Sb}$, considering only the objects with $C_{As} > 1\%$. One can observe that the samples LG14 and LG15 respect the proportionality of arsenic-silver, respectively arsenic-antimony, and one could make the interpretation that in the process of the manufacturing of the axes LG14, Dragu and LG15 Hoghiz, it was added a sulfoarsenate ore deliberately, to obtain axes of higher durity at a smaller temperature. The dagger LG41 does not respect this rule.

The axe LG10 and the chisel LG22 have about the same composition, they are tin-copper alloys, which are a superior type of bronze and they have also relatively the same values of concentrations for the others elements: Au, As and Sb, Ag and Ni. Although the axe LG10 contains concentrations of percents of zinc, the value $C_{Zn}=1310$ ppm is also a big concentration in comparison with the values of background for zinc, of the others copper objects, so that one

could say that also by the element Zn LG10 is synchronized with the object LG22, which contains $C_{Zn}=2.07\%$. Zinc is reported to be present in the copper object only accidentally. In the literature are given only some metallic finds of zinc⁷: at Dordos, also in Transylvania. The clusterisation of the 2 objects: axe LG10 and chisel LG22 on all the diagrams points out their strong association and indicates their possible common origin and manufacturing place.

As concerns **the axes from Valcele**, the request was to identify that the axes LG32 and LG33 belong to the Valcele hoard or are fakes, having a very different macroscopic aspect: these items have a dark brown color but the other axes from the same collection are covered by a large layer of light blue-greenish copper oxides. The elemental analyses show that the samples LG26, LG27, LG28, LG29, LG31, LG32, LG33 form a homogeneous group. The axe LG31 only contains a concentration of 74 ppm. The axes LG32 and LG33 exhibit values of concentrations very close to the others axes from Valcele. It could answer in the affirmative that the axes LG32 and LG33 are authentic.

The 2 objects found in Ariusd **the Needle LG40 and the Dagger LG41** are seemingly very different: the Needle is an unalloyed copper and the Dagger is prominent by its content of arsenic $C_{As}=1.53\%$, already discussed above, and also by its high concentration of Ag: $C_{Ag}=6230$ ppm. However the other trace elements: Sb, Se, Hg, Ni and especially Fe and Zn suggests the close association of these 2 objects. One could interpret the results of analyses for the Ariusd objects as follows: the needle and the Dagger seems to be manufactured from the same ore but it was added intentionally another ore with arsenic and silver.

The traces of Au and Ag in copper objects were represented in Fig. 3 It is known that there is a proportionality of the silver and gold concentrations both in the "sulfuric" and "oxides" copper ores^{2,4} Our samples follow relatively well the proportionality C_{Ag} with C_{Au} with the exception of the dagger from Ariusd.

Pendantivs "Large spiral", "Middle spiral" and "Small spiral" found in Cheile Aiudului, the samples LG37, LG38, LG39 present a similar structure: they are arsenic-bronzes and they are well grouped on the elements: Sb, Ag and Ni.

Sb presents random values of concentrations in the frame of analyzed samples. It is known that the antimony it is used to replace the tin. ^{10,11}. One can notice for Sb the high values of concentration for the pendantivs from Cheile Aiudului, the samples LG37, LG38, LG39, and also for the objects LG10 and LG22.

Dendograms. A study of the correlation of all the analyzed objects from the point of view of the whole compositional scheme was done using the dendogram tools. ^{12,13}. In Fig. 4 it is represented the dendogram of interdependence between the elements in the cooper samples. It comes in to view the levels of concentrations: I: Au is correlated with Ag the probability $P=19.5\%$, II: Au, Ag, As and Ni, with $P=17.0\%$, III: Au, Ag, As, Ni and Sb with $P=14.6\%$. In Fig. 5 it is shown the dendogram of correlation between all the analyzed copper objects from the point of view of all concentrations. These mathematical clustering must be seen cautiously and the obtained associations must be interpreted only together with historic data: place of found, dating, culture, typology ¹⁴.

References

1. E. Pernicka, Nucl. Instr. Meth., **14** (1986) 24-29
2. G. A. Wagner et al., "Arcäometllurgische Untersuchungen in Nordwest-anatolien", Vol. 31, 1984
3. Thomas C. Seeliger et al., Arcäometallurgische Untersucuchungen in Nord - und Ostanatolien, Jahrbuch der Römisch-Germanisches Zentralmuseums, Vol. 32, 1985
4. A. G. Wagner et al., Geochimische und Isotopische Charakteristika früher Rohstoffquellen für Kupfer, Blei, Silber und Gold in der Türkei, Jahrbuch der Römisch-Germanisches Zentralmuseums, Vol. 33, 1986
5. E. Pernicka, Erzlagerstätten in der Ägäis und ihre Ausbeutung im Altertum, Jahrbuch der Römisch-Germanisches Zentralmuseums, Vol. 34, 1987
6. A. M. Friedmann, "Copper artifacts: Correlations with Source Types of Copper Ores", Science, Vol 152, 1966
7. R. F. Tylecotte, "The technique and development of early copper smelting", A History of Metallurgy, Ed. The Metals Society, 1978
8. J. W. Mellor, A Comprihensive Treatise on Inorganic and Theoretical Chemistry, Vol. III, The History of Copper, 1956
9. Z. Goffer, Archaeolgical Chemistry, Chemical Analysis, Vol. 55, Eds. P.J. Elving, J.D. Winefordner, I.M. Kolthoff, John Wiley & Sons, 1980, p.211
10. P. T. Craddock, "The Copper alloys of Tibet and their Background", Occasional Paper, British Museum, No. 15, Eds. W. A. Oddy and W. Zwalf (1981)
11. P. T. Craddock, "Deliberate Alloying in the Atlantic Bronze Age", Proceedings of The Fifth Atlantic Colloquium", Dublin, 1978, p.369
12. D. Dumitrescu, "Hierarchical Pattern Classification", Fuzzy Sets Systems 28 (1988) p.145-162
13. I. Lup'sa and Gh. Lazarovici, Interdiscipl. Research Com. Seminar , Cluj

Univ., 19 Dec, 1985

14. C. Be'sliu, Gh. Lazarovici, A. Olariu, Acta Musei Porolissensis, Vol. XVI
(1992) p.97

FIGURE CAPTIONS

Fig. 1 Diagram of As content in the copper objects, by NAA

Fig. 2 Concentrations of As versus the concentrations of Sb or Ag for different ancient copper items, by NAA

Fig. 3 Concentration of Ag versus the concentration of Au for different ancient copper objects, by NAA

Fig. 4 Dendogram of interdependence between elements in ancient copper objects

Fig. 5 Dendogram of correlation of the copper objects

TABLE CAPTIONS

Table 1 List of analyzed copper objects from History Museum of Transylvania, Cluj-Napoca, by NAA

Table 2 Concentration of elements in different Neolithic copper objects, by NAA. The concentrations are expressed in ppm and for the values above 10 000 ppm, the results are given in %. The errors are generally $<7\%$.

Table 1.

Sample	Copper object	Nr. inv.	Place of found
LG1	Axe	P.837	Ugru'tiu
LG2	Axe-Pick-axe	P.838	Mico'slaca
LG3	Axe-Pick-axe	P.839	Cetatea de Balt'a
LG4	Pick-axe	P.840	'Sincai-Pogani
LG5	Battle Pick-axe	P.841	unknown
LG6	Axe	P.842	unknown
LG7	Axe-Pick-axe	P.843	Lacu, jud. Cluj
LG8	Axe-Pick-axe	P.844	region Cheile Turzii
LG9	Axe-Pick-axe	P.845	unknown
LG10	Axe	P.846	unknown
LG11	Axe-Pick-axe	P.847	unknown
LG12	Axe	P.848	col. Z. Torma
LG13	Pick-axe	P.850	unknown
LG14	Flat axe	P.851	Dragu
LG15	Chisel	P.852	Cold'au, zona Dej
LG16	Chisel	P.853	Hoghiz
LG17	Battle axe	P.854	P'adureni(=Be'seneu)
LG18	Pick-axe	P.855	Col. Z. Torma
LG19	Axe	P.856	unknown
LG20	Axe	P.857	unknown
LG21	Axe	P.859	Col. Z. Torma
LG22	Flat Chisel	I 2978	unknown
LG23	Bracelet	P.?	V 9558Col. Z. Torma
LG24	Bracelet	P.860	Cata, C. Petre'sti
LG25	Needle		Balomir
LG26	Axe	In 11	Vâlcele
LG27	Axe	10470	Vâlcele
LG28	Axe	10412	Vâlcele
LG29	Axe	I 10469	Vâlcele
LG30	Bead	8445	Decea Mure'sului
LG31	Axe		Vâlcele
LG32	Axe		Vâlcele
LG33	Axe		Vâlcele
LG34	Small needle	VI 1399=JUNGH	Decea Mure'sului
LG35	Bead	VI 1293	Decea Mure'sului
LG36	Necklace VI	1300=JUNGH 9024	Decea Mure'sului
LG37	Large spiral		Cheile Aiudului
LG38	Middle spiral		Cheile Aiudului
LG39	Small spiral		Cheile Aiudului
LG40	Needle	III 1789	Ariu'sd, Covasna
LG41	Dagger	III 378	Ariu'sd, Covasna

Table 2.

Sample	Au	As	Sb	Se	Hg	Cr	Ag	Ni	Sc	Fe	Zn	Co	Ta	Sn
LG1	0.52	22	8.63	7.6	2.74	<2.4	32.7	99	0.039	150	19.2	–	0.13	180
LG2	<0.54	–	2.12	<2.4	1.28	–	8.27	68	–	–	15.8	9.3	0.15	–
LG3	0.81	–	11.4	24	–	–	47.4	40	–	–	–	6.2	1.18	–
LG4	0.69	–	4.8	1.5	2.35	–	21.6	35.5	0.021	130	14.3	–	–	100
LG5	1.9	110	2.94	2.9	2.49	–	8.04	40.7	0.019	22	12	–	0.2	60
LG6	0.62	–	43.5	77.4	2.39	–	119	48	–	–	39.4	–	–	260
LG7	8.1	–	11.9	<5.1	1.9	–	38.2	100	–	–	14	–	–	403
LG8	0.66	127	6.72	<5.1	<1.7	–	37.5	42	0.031	500	35.4	–	–	390
LG9	0.39	54	3.88	2	0.43	–	31.6	41.4	0.087	370	20.7	–	–	96
LG10	12.7	2820	1220	24	0.8	–	913	370	0.198	–	10	410	–	1.11%
LG11	0.69	14	4.34	3.6	–	–	16.4	33	0.014	340	18	5.2	0.29	–
LG12	<0.75	24	1.24	2.5	–	–	5.4	47.1	0.03	–	13	6.1	0.18	–
LG13	–	48	1.76	–	1.9	5.5	3.5	50	0.05	380	23	1.6	0.4	–
LG14	4.4	2.61%	85.5	37.4	–	–	163	85	0.04	540	28	–	–	–
LG15	3.4	1.68%	20.5	48.8	–	–	54.9	68.9	0.02	–	19.3	–	–	–
LG16	9.2	6270	10.4	8.4	1.9	–	378	23	–	–	28	–	0.87	–
LG17	–	–	2.36	11.7	–	–	10	53	–	–	29	8.6	0.97	–
LG18	–	–	0.72	–	–	–	4.8	49	–	400	25	16.7	0.25	–
LG19	<1.5	–	10.5	17	–	–	39.3	120	0.05	–	36	32.2	2.31	–
LG20	27.8	–	5.18	89.5	1.96	–	94.6	184	0.04	–	21	–	1.37	–
LG21	11.7	550	18.3	13.9	1.28	–	256	–	–	–	34	8.8	0.53	–
LG22	10.9	1540	2040	–	–	–	925	1210	–	–	2.07%	7.8	–	2.82%
LG23	8.8	–	3.36	19.6	1.55	–	381	47	–	–	22	27.6	2.2	–
LG24	0.32	19	3.1	1.4	0.43	<1.6	17.9	43.9	–	–	31.9	–	0.19	–
LG25	–	–	8.53	–	<4.7	11	39.8	110	–	660	30	–	1.9	–
LG26	1.4	–	1.23	14.4	–	–	69.5	47.7	0.02	–	93	–	0.22	–
LG27	0.8	–	3.55	<4.6	0.67	4	31.7	56.5	0.1	–	13	–	–	–
LG28	1.4	–	4.37	13.7	0.417	–	81.5	63.9	0.03	–	18	11.3	0.82	–
LG29	3.2	–	4.76	22.7	1.57	–	114	64	–	–	–	–	–	–
LG30	1	–	6.69	3.8	1.7	–	53.8	55.2	0.02	–	26	–	0.3	–
LG31	3.4	74	5.88	11	2.4	–	60.2	51	0.03	–	25	–	–	–
LG32	1.62	–	11.8	9.3	1.65	–	97.5	47.9	0.02	–	19	–	–	–
LG33	0.9	–	2.87	9.1	0.96	–	63.5	24	–	–	15	–	–	–
LG34	<0.4	–	1.68	9.73	2.09	–	6.21	32.4	0.054	150	25.3	–	–	–
LG35	2.76	–	14.2	2.3	0.926	1.3	27.1	67.7	0.115	1140	16.8	–	0.08	60
LG36	–	–	3.63	–	8.8	–	23	–	0.15	1300	160	–	2	–
LG37	25.9	3600	548	181	8.46	–	307	330	–	–	–	10	–	–
LG38	7.5	3250	307	71.5	2.5	–	97.5	419	0.56	–	140	2	–	–
LG39	4.7	1300	634	–	55	–	155	150	0.08	–	755	12	–	–
LG40	–	–	2.58	17.9	8.5	–	4.82	173	8.03	690	39	2.7	–	–
LG41	<0.9	1.53%	12.3	12	4.4	–	6230	92	–	850	68	–	–	–

Arsenic, ppm

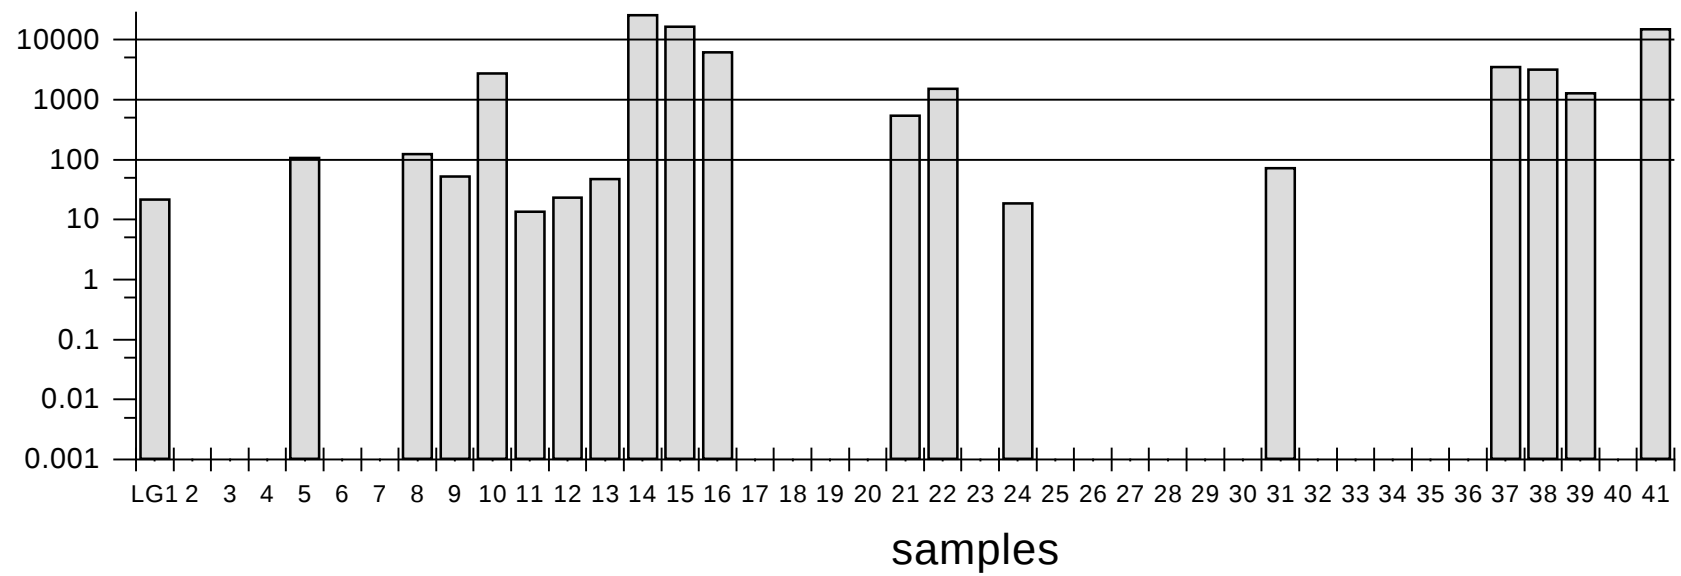


Fig. 1

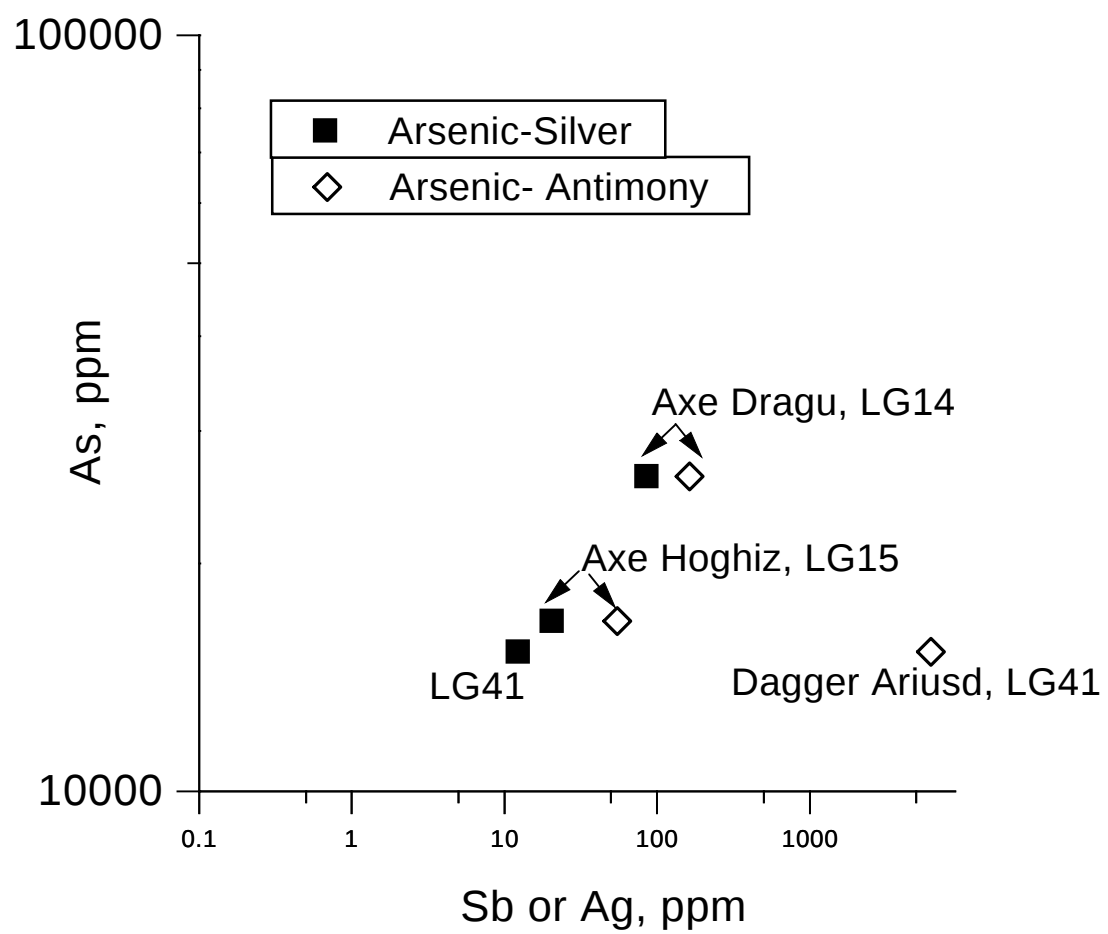


Fig. 2

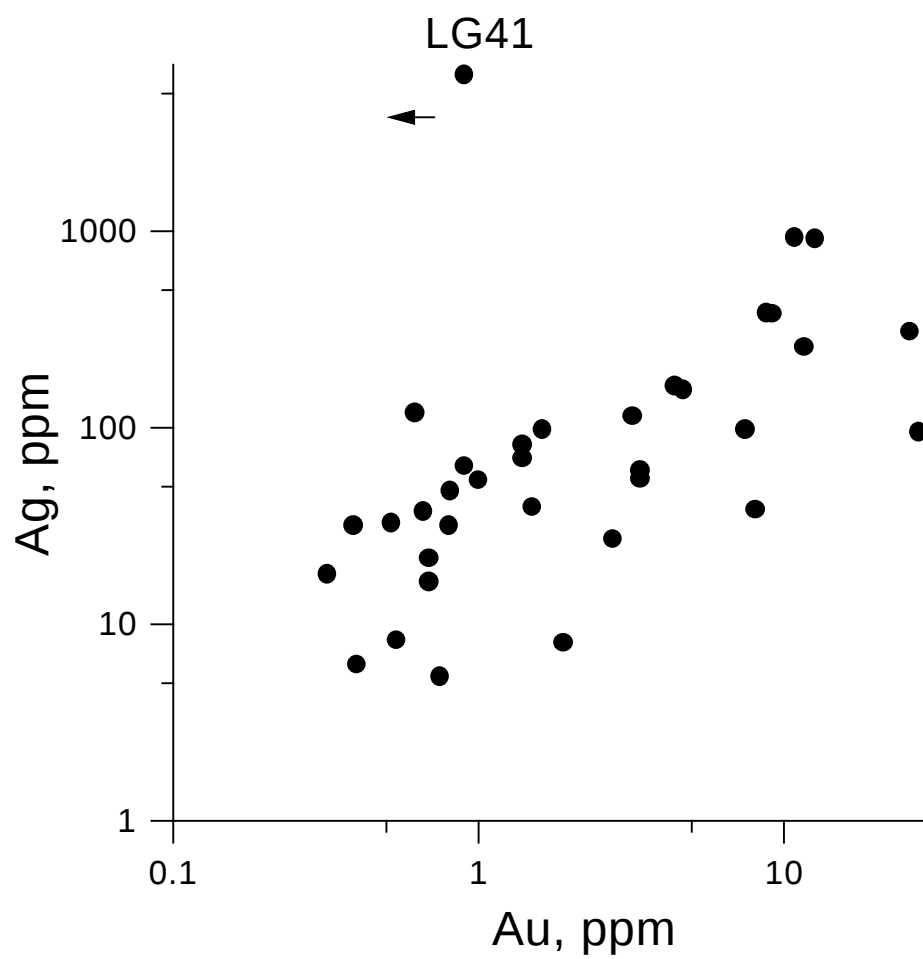


Fig. 3

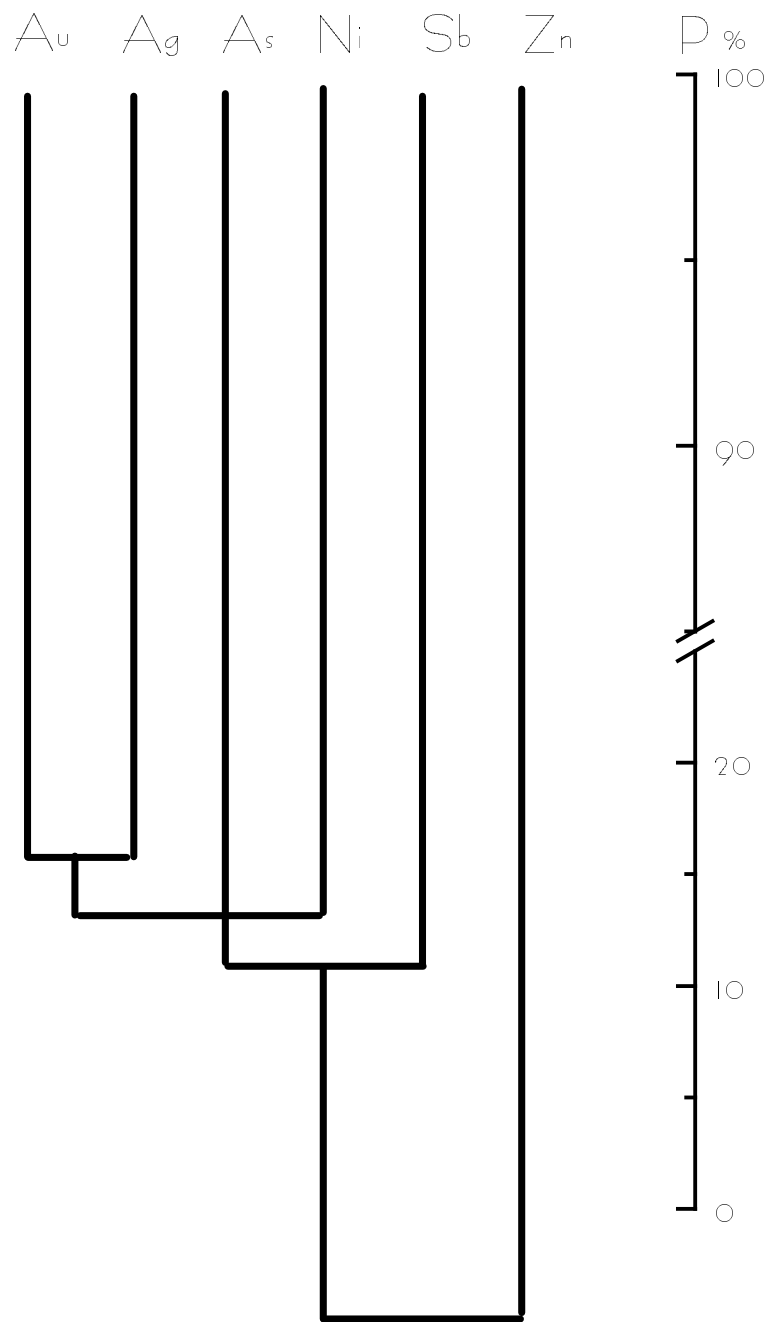


Fig. 4

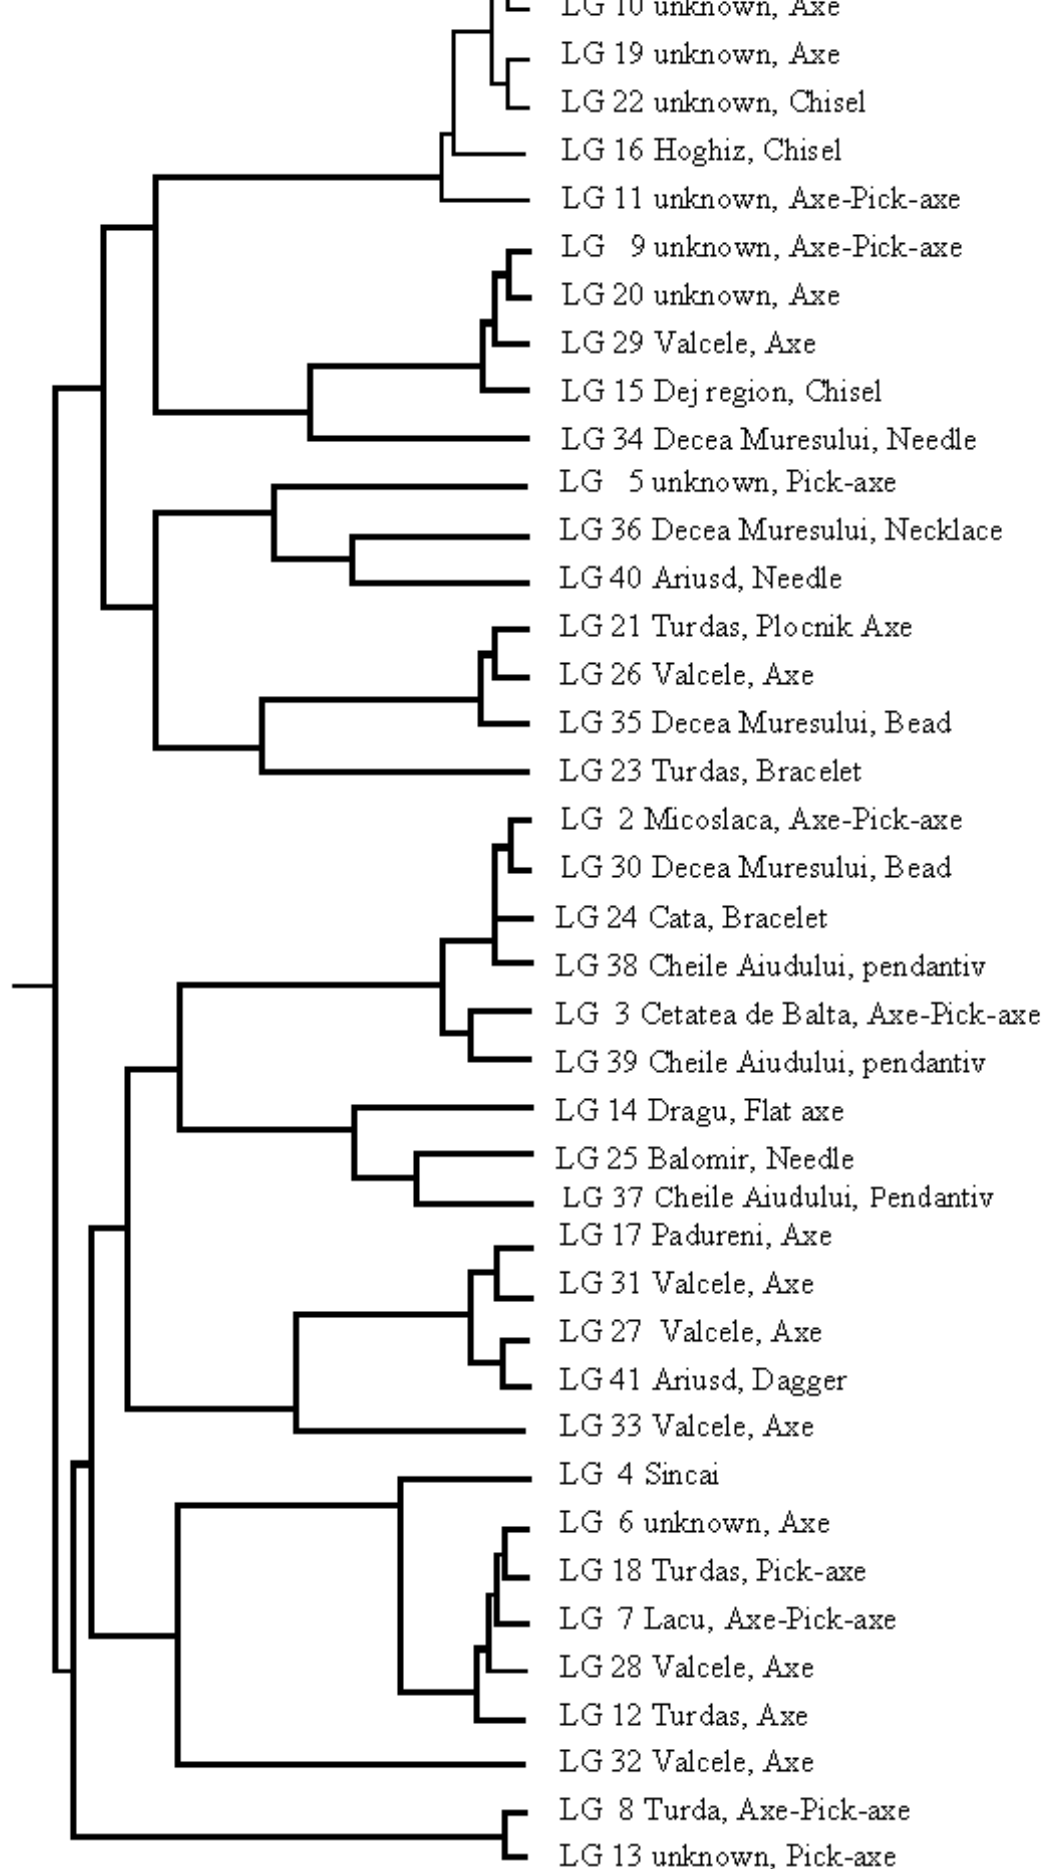


Fig. 5

0 10 20 30 40 50 60 70 80 90 100 P, %

